

# IOWA STATE UNIVERSITY

## Digital Repository

---

Chemistry Publications

Chemistry

---

4-2003

## The effect of common gases on nucleation of metal islands: The role of oxygen in Ag(100) homoepitaxy

Anthony R. Layson

*Iowa State University*

James W. Evans

*Iowa State University, [evans@ameslab.gov](mailto:evans@ameslab.gov)*

V. Fournée

*Iowa State University*

Patricia A. Thiel

*The Ames Laboratory (U.S. Department of Energy) and Iowa State University, [thiel@ameslab.gov](mailto:thiel@ameslab.gov)*

Follow this and additional works at: [http://lib.dr.iastate.edu/chem\\_pubs](http://lib.dr.iastate.edu/chem_pubs)



Part of the [Chemistry Commons](#), and the [Mathematics Commons](#)

The complete bibliographic information for this item can be found at [http://lib.dr.iastate.edu/chem\\_pubs/94](http://lib.dr.iastate.edu/chem_pubs/94). For information on how to cite this item, please visit <http://lib.dr.iastate.edu/howtocite.html>.

---

This Article is brought to you for free and open access by the Chemistry at Iowa State University Digital Repository. It has been accepted for inclusion in Chemistry Publications by an authorized administrator of Iowa State University Digital Repository. For more information, please contact [digirep@iastate.edu](mailto:digirep@iastate.edu).

---

# The effect of common gases on nucleation of metal islands: The role of oxygen in Ag(100) homoepitaxy

## Abstract

Preexposure to molecular oxygen gas,  $O_{2,g}$ , can have a strong effect on the nucleation and growth of Ag islands on Ag(100) at 250 K. At this temperature, molecular oxygen dissociates efficiently at kink sites on steps. Subsequent deposition of Ag produces a far lower density of  $Ag_{ad}$  islands than without oxygen. There is an associated increase in the Ag flux-scaling exponent, from 0.28 for the oxygen-free surface to 0.9 for the preexposed surface. Two-step deposition experiments show that species containing atomic oxygen diffuse freely across terraces and steps at this temperature and on the time scale of deposition. We hypothesize that the nucleating species contains both Ag and O, and that nucleation of islands is highly reversible (~critical size  $i > 1$ ). The diffusion of small islands, if it occurs, is not sufficient to explain the data.

## Keywords

adsorption, chemical bonds, deposition, dissociation, epitaxial growth, low energy electron diffraction, molecular dynamics, oxygen, scanning tunneling microscopy, silver, single crystals, homoepitaxy, Ames Laboratory

## Disciplines

Chemistry | Mathematics

## Comments

The following article appeared in *Journal of Chemical Physics* 118, 14 (2003): 6467 and may be found at doi:[10.1063/1.1558035](https://doi.org/10.1063/1.1558035).

## Rights

Copyright 2003 American Institute of Physics. This article may be downloaded for personal use only. Any other use requires prior permission of the author and the American Institute of Physics.

# The effect of common gases on nucleation of metal islands: The role of oxygen in Ag(100) homoepitaxy

A. R. Layson, J. W. Evans, V. Fournée, and P. A. Thiel<sup>a)</sup>

*Departments of Chemistry and Mathematics, and Ames Laboratory, Iowa State University,  
Ames, Iowa 50011*

(Received 20 September 2001; accepted 13 January 2003)

Preexposure to molecular oxygen gas,  $O_{2,g}$ , can have a strong effect on the nucleation and growth of Ag islands on Ag(100) at 250 K. At this temperature, molecular oxygen dissociates efficiently at kink sites on steps. Subsequent deposition of Ag produces a far lower density of  $Ag_{ad}$  islands than without oxygen. There is an associated increase in the Ag flux-scaling exponent, from 0.28 for the oxygen-free surface to 0.9 for the preexposed surface. Two-step deposition experiments show that species containing atomic oxygen diffuse freely across terraces and steps at this temperature and on the time scale of deposition. We hypothesize that the nucleating species contains both Ag and O, and that nucleation of islands is highly reversible (critical size  $i \geq 1$ ). The diffusion of small islands, if it occurs, is not sufficient to explain the data. © 2003 American Institute of Physics.

[DOI: 10.1063/1.1558035]

## I. INTRODUCTION

As trends in technology advance to ever-smaller scales, the production and control of nanoscale structures becomes increasingly important, and the sensitivity to contamination becomes increasingly critical. Contamination from common background gases can never be eliminated entirely, even in the cleanest environments. However, this disadvantage may also be turned to advantage: If the effects of adsorbed gases are sufficiently understood, they can be used as deliberate tools in controlling nanostructure morphology. Indeed, surfactants have drawn much interest because of their ability to alter the *vertical* atomic-scale morphology of deposited films, i.e., to enhance layer-by-layer growth.<sup>1–10</sup> A related phenomenon is the effect of adsorbates, including surfactants, on the *lateral* (in-plane) morphology that is typically controlled by nucleation and growth of islands during metal deposition.<sup>4,5,10–12</sup> In this paper, we focus specifically on Ag(100) homoepitaxy, since this is a simple model system in which the pure-film characteristics are well understood.<sup>13</sup> Furthermore, we concentrate on the lateral morphology at low coverages of Ag, thereby gaining insights specifically into the nucleation process.

Other studies indicate that the effect of common adsorbed gases on lateral structure in metal homoepitaxy may be a rich topic. For example, the presence of  $CO_{ad}$  affects the size, shape, and density of islands formed in deposition of Pt/Pt(111).<sup>14</sup> The presence of  $O_{ad}$  on Ni(100) causes the rotation and elongation of Ni islands formed via Ni deposition.<sup>15</sup>

Here, we show that exposing Ag(100) to  $O_{2,g}$  prior to Ag deposition interferes with the initial nucleation of Ag islands. As a result, the use of  $O_{2,g}$  provides a means to control the size and density of these islands. We also examine the

underlying processes by which  $O_{ad}$  interacts with the Ag atoms.

Much is known about the interaction of  $O_{2,g}$  with the Ag(100) surface from the extensive studies of Valbusa and co-workers.  $O_{2,g}$  is quite unreactive to Ag(100), with a sticking probability of  $10^{-4}$  at 300 K.<sup>16</sup>  $O_{2,g}$  adsorbs with higher probability and dissociates at kink sites on steps.<sup>17–20</sup> The rate for dissociation of  $O_{2,g}$  is, in fact, determined by the population of kink sites. The resultant  $O_{ad}$  is very stable on the (100) surface, as it does not recombine and desorb molecularly at higher temperature.<sup>17</sup> We assume that this process—dissociation at kink sites—generates the oxygen-containing species that so strongly affects nucleation on Ag(100), as reported in this study.

Our own studies of relaxation processes in Ag/Ag(100) films after growth<sup>21,22</sup> are highly relevant as well, since some of the atomic-scale processes operative in relaxation are also involved in nucleation and growth. Relaxation occurs because nucleation and growth is a kinetically governed process, producing nonequilibrium features that then evolve with time toward equilibrium. For instance, any ensemble of islands will evolve (coarsen) toward larger average size and lower density. Elsewhere<sup>21,22</sup> we have shown that exposure to  $O_{2,g}$  accelerates and changes the mechanism of coarsening of Ag islands on Ag(100) after nucleation and growth, and that dissociation of  $O_{2,ad}$  is necessary for this to occur.

## II. EXPERIMENTAL DETAILS

Our experiments were performed in a ultrahigh vacuum (UHV) chamber with base pressure  $< 1 \times 10^{-10}$  Torr, and a typical pressure during experiments of  $\approx 1 \times 10^{-10}$  Torr. The sample was cleaned by repeated cycles of  $Ar^+$  sputtering (20 min, 500 V,  $T \approx 300$  K) followed by annealing at 700 K. Oxygen treatments [500 langmuir, L ( $1 \text{ L} = 10^{-6} \text{ Torr s}$ ) 700 K] were performed periodically and were useful in removing the last remnant of contamination from the surface. No re-

<sup>a)</sup>Author to whom correspondence should be addressed. Electronic mail: thiel@ameslab.gov

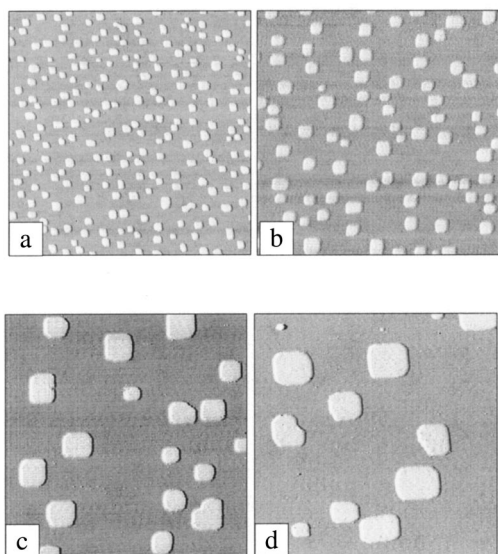


FIG. 1. Ag islands on a Ag(100) surface exposed to various amounts of oxygen prior to deposition at 250 K. Exposures in units of langmuirs (L): (a) 0 L (clean), (b) 5 L, (c) 15 L, (d) 30 L. The deposition flux for all images was 0.002 ML/s. All images span  $125 \times 125 \text{ nm}^2$ .

sidual oxygen could be detected after these treatments. This was confirmed through the reproduction of known experimental results on the oxygen-free surface. Evaporative deposition of Ag onto the Ag(100) single-crystal surface was usually performed at  $T \leq 250 \text{ K}$ . The surface was exposed to  $\text{O}_{2,g}$  by backfilling the chamber to  $\sim 10^{-8}$  Torr in continuous flow. Unless noted otherwise, all exposures were conducted at the same temperature as Ag deposition. Temperature variations were minimal, with fluctuations of no more than  $\pm 1 \text{ K}$  throughout the duration of the experiment. Island evolution was monitored with an Omicron variable-temperature scanning tunneling microscope (VTSTM). Some complementary studies were performed with an Omicron instrument for high-resolution low-energy electron diffraction (HRLEED).

### III. RESULTS AND INTERPRETATION

#### A. Submonolayer deposition

Figure 1 shows a series of scanning tunneling microscope (STM) images from an experiment where clean Ag(100) was exposed to various amounts of  $\text{O}_{2,g}$  prior to the deposition of 0.2 monolayers (ML) of Ag. The images show that exposure to  $\text{O}_{2,g}$  prior to Ag deposition affects the nucleation and growth of Ag islands. Increasing the  $\text{O}_{2,g}$  preexposure results in a decrease in island density (and a corresponding increase in island size).

Based upon work by others, and as mentioned in Sec. I, we infer that exposure to  $\text{O}_{2,g}$  results in adsorption and dissociation at kink sites along steps. However, if the dissociated oxygen remained trapped at the kink sites, it could not affect nucleation and growth of Ag islands in the centers of broad terraces, in contrast to observations here.<sup>23</sup> Hence, an  $\text{O}_{ad}$ -containing species must be able to leave the kink sites and diffuse across the terraces, on the time scale of deposition (and the shorter time scale of nucleation) at 250 K.

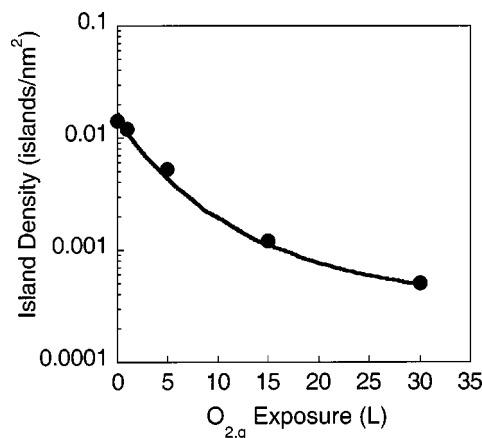


FIG. 2. Variation of average island density,  $N_{av}$ , with  $\text{O}_{2,g}$  preexposure, at fixed temperature (250 K) and fixed flux.

Buatier de Mongeot *et al.* also concluded that  $\text{O}_{ad}$  does not remain trapped at kink sites after dissociation.<sup>17</sup>

Figure 2 shows the quantitative variation of average island density,  $N_{av}$ , with  $\text{O}_{2,g}$  preexposure, at fixed temperature (250 K) and fixed flux.  $N_{av}$  falls nonlinearly but smoothly from its value at zero exposure to its value at 30 L preexposure. At 30 L, a plateau has not yet been reached but is being approached. We interpret this to mean that increasing exposure to  $\text{O}_{2,g}$  interferes with (and inhibits) the simple nucleation scenario. It is likely replaced by a more complex pathway characterized by an effective critical size that increases and finally saturates with  $\text{O}_{2,g}$  exposure (see Sec. IV).

An upper limit on the coverage of oxygen in our experiments is probably given by the work of Rocca *et al.*, wherein the coverage was estimated from vibrational experiments to be about 0.04 ML at 250 K on Ag(100), after an  $\text{O}_{2,g}$  exposure of 1000 L.<sup>24</sup> The coverage of oxygen on our surface is too low to be detectable with Auger electron spectroscopy.

Classic nucleation theory<sup>25–28</sup> shows that the island density should scale with the experimental parameters of flux  $F$  and temperature  $T$  according to

$$N_{av} \propto F^\chi e^{-E/kT}. \quad (1)$$

Examining first the flux dependence, Fig. 3 shows the variation of  $N_{av}$  at 250 K, as determined by STM, for (a) zero preexposure to  $\text{O}_{2,g}$  and (b) 30 L preexposure to  $\text{O}_{2,g}$ . The linear variation of the data are in accord with Eq. (1). From the slopes of the straight lines shown in Fig. 3, the value of  $\chi$  is 0.28 for the surface with no preexposure to  $\text{O}_{2,g}$ . This is consistent with our previous results for the clean surface.<sup>29</sup> With 30 L preexposure to  $\text{O}_{2,g}$ , however, there is a large increase in the scaling exponent, to about 0.9.

The value of  $\chi$  depends upon the nucleation mechanism and upon the degree of mobility of very small islands (relative to monomers). The value of 0.28 for the clean surface indicates irreversible island formation (critical size of 1), with no significant mobility of small islands. The larger value of  $\chi$  for the lower curve in Fig. 3 indicates that the presence of  $\text{O}_{ad}$  containing species destabilizes very small islands, hence increasing the critical size; it may also induce significant mobility in small Ag islands. Note that in conven-

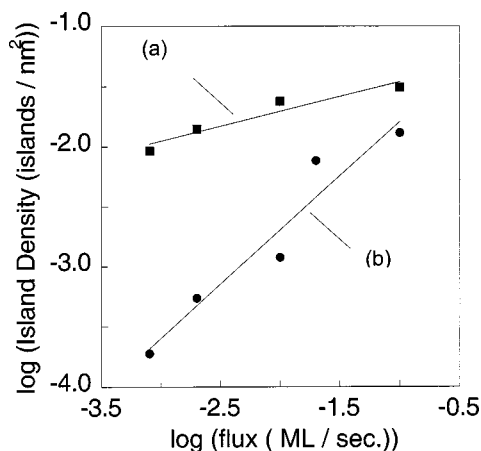


FIG. 3. Island density vs deposition flux for 0.2 ML Ag/Ag(100) at 250 K for (a) O-free surface and (b) surface preexposed to 30 L O<sub>2</sub>.

tional nucleation theory,  $\chi$  has a theoretical upper limit of unity for highly reversible island formation,<sup>25,26,30</sup> and higher preexposures of O<sub>2,g</sub> could presumably have pushed the value of  $\chi$  even closer to this limit, as implied by Fig. 2.

Equation (1) shows that island density should scale with temperature as well as flux, and should thus yield the parameter  $E$ . Figure 4 shows the experimental variation in  $N_{av}$  after deposition of 0.2 monolayers of Ag. Curve (a) in Fig. 4 corresponds to data collected previously for the clean surface.<sup>31</sup> [However, the values shown in Fig. 4 have been adjusted according to Eq. (1) to allow direct comparison to the new data, since the two data sets were acquired with different fluxes.] Curve (b) in Fig. 4 corresponds to a 30 L preexposure to O<sub>2,g</sub>, for each temperature. It can be seen that curves (a) and (b) are almost parallel between 300 and 210 K, with curve (b) always lying beneath curve (a) in this temperature range. The relative position of the two lines between 300 and 210 K simply means that, at any given temperature, the island density is always lower in the presence of oxygen than in the absence, as expected from the foregoing discussion. According to Eq. (1), the slope can be used to derive an

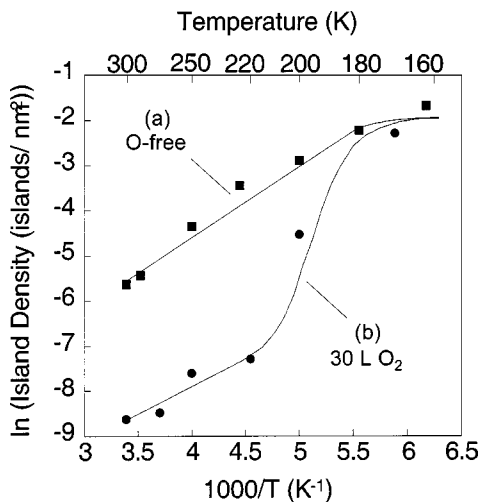


FIG. 4. Arrhenius plot for 0.2 ML Ag/Ag(100) for (a) the O-free surface and (b) surface preexposed to 30 L O<sub>2</sub>.

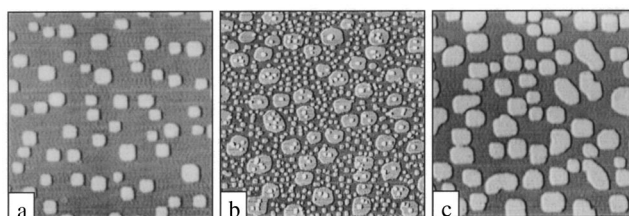


FIG. 5. STM image (a) taken after deposition of 0.2 ML Ag/Ag(100) at 320 K. Image (b) taken after a second deposition of 0.2 ML Ag at 250 K, on the surface shown in (a). Image (c) taken after the surface in (a) was exposed to 30 L O<sub>2</sub>, followed by a second deposition of 0.2 ML of Ag at 250 K. The flux for the first and second depositions were 0.002 ML/s and 0.02 ML/s, respectively. All images span 175×175 nm<sup>2</sup>.

apparent energy,  $E$ . In the temperature range of 300–220 K, the slope corresponds to  $E=0.10$  eV in curve (b), and  $E=0.13$  eV in curve (a). The physical significance of these energies will be discussed in Sec. IV.

In Fig. 4, curve (b) undergoes a transition, between 210 and 180 K, in which the island density increases rapidly and finally links up with the value for curve (a). At even lower temperatures, island densities match closely for the two curves. Dissociation of molecular oxygen is not active below 180 K. This explains the merger of the two curves below 180 K, and demonstrates again that O<sub>ad</sub> or something that contains O<sub>ad</sub> must be the chemical species that interferes with nucleation and growth, rather than O<sub>2,ad</sub>. In other words, O<sub>2,ad</sub> must dissociate before its effect can be observed.

The requirement of O<sub>2,ad</sub> dissociation at kinks implies that the density of steps is important. In fact, this is supported by experiments in our laboratory, in which two Ag(100) crystals were compared, albeit with different techniques, as follows. We performed HRLEED experiments on a different crystal than the one used in all of the STM experiments. Like STM, HRLEED provides a measure of average island densities, and in our past work we have shown that HRLEED data are quantitatively comparable to STM data, for clean Ag(100) homoepitaxy.<sup>32</sup> In the new HRLEED experiments, preexposure to oxygen had no measurable effect on subsequent Ag island densities.

We attribute this to the feature that the global average of the step density for the HRLEED sample is much lower than for the STM sample. More specifically, HRLEED profiles indicate a broad terrace with a mean width of about 50 nm, a value which corresponds to a global average over the electron beam diameter of  $\sim 1$  mm. For the STM sample, all our images and data analysis correspond to a carefully selected broad terrace spanning several tens of nanometers in width. However, such broad terraces are rare. Globally, the STM sample is much rougher than the HRLEED sample, with much higher global step (and kink) density and many regions of rough topography. We believe that this global sample morphology controls the overall oxygen uptake. Thus oxygen must readily adsorb in these rough regions on the STM sample and diffuse to the few broader terraces.



## B. Multilayer deposition studies

Figure 5 shows the results from an experiment in which the final surface films are created through two separate Ag deposition steps. The first step is deposition of 0.2 ML of Ag at 320 K, without preexposure to  $O_{2,g}$ , and at a relatively low flux of 0.002 ML/s. This relatively high temperature and low flux results in large islands, rather homogeneous in shape and size,<sup>33</sup> as shown in Fig. 5(a). The second step is deposition of additional Ag (another 0.2 ML) at a lower temperature, 250 K, and at ten times higher flux, 0.02 ML/s. In the absence of  $O_{ad}$ , this produces much smaller islands, on the terrace regions between as well as on top of the previously created large islands, as shown in Fig. 5(b).

Figure 5(c) shows a surface that was exposed to 30 L of  $O_{2,g}$ , at 250 K, between the first and second Ag depositions. The result is that during the second Ag deposition, no additional islands form, either between or on top of the islands generated by the first deposition. With  $O_{ad}$ -containing species present, all Ag atoms deposited in the second treatment must have diffused to preexisting step edges; in particular, nucleation on top of islands is eliminated.

## IV. DISCUSSION

The main issue to be resolved is the mechanism by which the presence of  $O_{ad}$  interferes with the nucleation and growth of Ag islands on Ag(100). Several possibilities emerge. Although we cannot unambiguously determine which of these applies, we discuss one plausible scenario for the saturation regime of 30 L exposure to  $O_{2,g}$ , and comment on other possibilities. Two key pieces of experimental data which guide our discussion are that the island density,  $N_{av}$ , is described by Eq. (1) with a high flux scaling exponent,  $\chi = 0.9$  (indicating highly reversible island formation), and a low effective energy,  $E \approx 0.10$  eV, in the presence of oxygen.


In traditional nucleation theory, a single species with terrace diffusion barrier,  $E_d$ , nucleates islands with critical size,  $i$ . This means that islands of more than  $i$  atoms are effectively stable on the time scale of island growth during deposition, but smaller islands can dissociate; islands of  $i$  atoms have a finite binding energy,  $E_b$ . Under these conditions, the energy  $E$  in Eq. (1) is given by

$$E \approx \chi \left( E_d + \frac{E_b}{i} \right), \quad \text{where } \chi \approx \frac{i}{i+2}. \quad (2)$$


For the clean  $Ag_{ad}/Ag(100)$  system, where  $i = 1$  (so  $E_b = 0$ ),  $\chi \approx 0.28$  (showing an expected<sup>27,28</sup> slight deviation from the asymptotic theoretical value of  $1/3$ ), and  $E = 0.13$  eV. Thus, one concludes that  $E_d(Ag_{ad}) = E/\chi = 0.45$  eV. This value of  $E_d(Ag_{ad})$  is in agreement with the range of previous theoretical and experimental determinations, 0.37 to 0.45 eV.<sup>29,31–35</sup> For the case with 30 L  $O_{2,g}$ , if  $Ag_{ad}$  diffusion were to play a significant role in island nucleation, such a high  $E_d$  would be inconsistent with the similar low value of  $E$  but much larger  $\chi$  [assuming that  $E$  is determined by some formula such as Eq. (2), even in this more complex case]. This prompts the following model, in which we postulate that a species other than  $Ag_{ad}$  plays the key role in island nucleation. This species is likely of the form  $Ag_mO_{ad}$ .

## A. Island nucleation mediated by an $Ag_mO_{ad}$ species

As we discuss in Sec. III A and also below, it is clear that an oxygen-containing species can readily detach from step edges, and likely also from far-removed faceted regions of the sample, to populate the terrace of interest. We expect that the population of this species on terraces is determined by an attachment–detachment equilibrium, and that this population is relatively high for 30 L exposure to  $O_{2,g}$ . Suppose for the moment that this detaching species is  $O_{ad}$ . Then, since  $Ag_{ad}$  does not play a significant role in island nucleation, we propose that newly deposited  $Ag_{ad}$  is quickly captured by  $O_{ad}$  to form a diffusing  $AgO_{ad}$  species, which mediates island nucleation. Islands thus formed are destabilized by a large population of incorporated  $O_{ad}$ . Formation of stable islands requires a sufficiently large number of  $Ag_{ad}$  atoms (large  $i$ ), and expulsion of a sufficient amount of  $O_{ad}$ . In this picture, one has  $Ag_mO_{ad} = AgO_{ad}$ , i.e.,  $m = 1$ . Schematically, we write

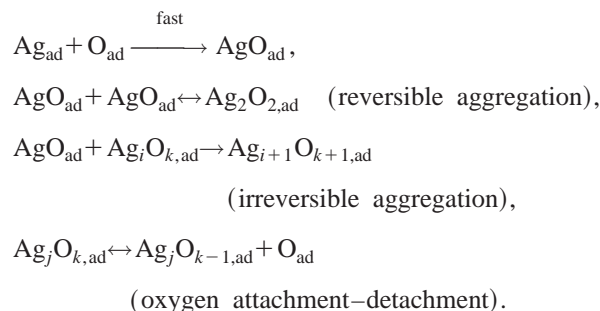

Here,  $\rightarrow$  and  $\leftrightarrow$  denote irreversible and reversible steps, respectively. If the species readily detaching from step edges were actually  $AgO_{ad}$  rather than  $O_{ad}$ , then the above would be replaced by  $Ag_mO_{ad} = Ag_2O_{ad}$ , i.e.,  $m = 2$ , and schematically

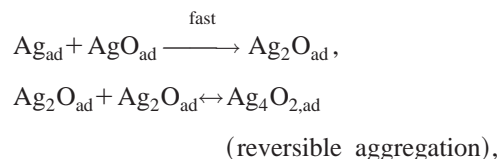

etc.

Returning to the experimental results, and adopting the standard formula (2), one concludes that  $i \approx 20$ , and that an upper bound on the terrace diffusion barrier,  $E_d$ , for  $Ag_mO_{ad}$  is provided by  $E/\chi = 0.10/0.9 = 0.11$  eV, which is far below  $E_d(Ag_{ad}) = 0.45$  eV. Of course, one should be cautious regarding the use of Eq. (2) for the complex island formation process above. Furthermore, in reality, there is not a single critical size, since presumably Ag islands with less  $O_{ad}$  will be stable at smaller sizes, reaching  $i = 1$  in the limit of no  $O_{ad}$ . Thus, the critical size above should be regarded as an effective or average value.

## B. Alternative scenarios

(i) One might consider that the rate of terrace diffusion for  $Ag_{ad}$  could be enhanced by the presence of an oxygen-containing adsorbate, without direct bonding between  $Ag_{ad}$  and the other adsorbate. However, it seems unlikely that such

interactions could reduce the terrace diffusion barrier by a factor of 4 or more, to 0.1 eV or below, which would be required for a model in which island nucleation was mediated by diffusion of  $\text{Ag}_{\text{ad}}$ . This is particularly true in light of the low oxygen coverage.

(ii) Equation (2) actually applies only in situations where stable nuclei are relatively immobile. If this condition is not met,  $\chi$  can increase to a maximum value of 0.5 for irreversible formation ( $i=1$ ) of mobile nuclei.<sup>36–40</sup> Hence, while mobility of small nuclei cannot be ruled out—and is made somewhat plausible by a recent postulate of adsorbate-enhanced mobility for Cu trimers decorated by sulfur on the Cu(111) surface,<sup>41,42</sup>—this effect alone could not explain the experimental value of  $\chi=0.9$ . Reversibility in island formation is necessary (as well as nucleation mediated by a rapidly diffusing species).

(iii) The picture of newly deposited  $\text{Ag}_{\text{ad}}$  being efficiently captured by  $\text{O}_{\text{ad}}$  (or  $\text{AgO}_{\text{ad}}$ ) is an oversimplification. This is certainly the case for exposures of  $\text{O}_{2,\text{g}}$  below 30 L or for low  $T$ , where the equilibrium population of  $\text{O}_{\text{ad}}$  (or  $\text{AgO}_{\text{ad}}$ ) on the terraces is lower. Equivalently, in the low-exposure or low- $T$  regimes, one can say that the concentration of  $\text{O}_{\text{ad}}$  is not high enough to drive the reaction  $\text{Ag}_{\text{ad}} + \text{O}_{\text{ad}} \xrightarrow{\text{fast}} \text{AgO}_{\text{ad}}$  entirely to the right, either for kinetic or thermodynamic reasons. In these regimes, eventually one must cross over to the picture for island nucleation in the clean Ag/Ag(100) system.

### C. Interterrace diffusion of $\text{Ag}_m\text{O}$

Another issue is whether the  $\text{O}_{\text{ad}}$ -containing species can move freely between terraces, on the time scale of our experiments. This is clarified by the experiments of Fig. 5. The lack of island nucleation on the large islands, after  $\text{O}_{2,\text{g}}$  pre-exposure and the second deposition of Ag [Fig. 5(c)], shows that the  $\text{O}_{\text{ad}}$ -containing species must be able to move to the tops of these islands, which is equivalent to moving from a lower terrace to an upper terrace on the extended surface. The nucleating species must also be able to get off the island tops again, or else it would nucleate there. Getting off an island is equivalent to moving from an upper terrace to a lower terrace on the extended surface.

It could be argued that, in the experiments of Fig. 5, the  $\text{O}_{\text{ad}}$ -containing species does not cross upward at all, but rather helps  $\text{Ag}_{\text{ad}}$  move downward. That is to say, the  $\text{O}_{\text{ad}}$ -containing species might lower the step-edge barrier for downward transport of  $\text{Ag}_{\text{ad}}$  that lands on top of islands in the second deposition. For clean Ag(100) homoepitaxy, there is a small extra barrier of  $\approx 70$  meV to downward diffusion of  $\text{Ag}_{\text{ad}}$  on the close-packed  $\langle 110 \rangle$ -type steps.<sup>43,44</sup> is zero on the most open  $\langle 001 \rangle$ -type steps. However, this argument is not viable because the experimental conditions in Fig. 5(c) (high flux, large preexisting islands, and low temperature) are such that second layer nucleation would still be expected, even if the step-edge barrier for  $\text{Ag}_{\text{ad}}$  were zero everywhere (as confirmed by simulations).<sup>45</sup> Hence, the species that detach from the steps and that combine with  $\text{Ag}_{\text{ad}}$  to mediate nucleation must be able to ascend and descend steps freely at these temperatures and on the time scale of deposition.

### D. Steps as dissociation sites for $\text{O}_{2,\text{g}}$

Comparing the results for two different samples, one with higher step density than the other, shows that steps are extremely important in providing sites where the active species are generated (Sec. III A), and that step densities can affect the reproducibility of results from sample to sample. This probably also accounts for the fact that, in previous work, we reported that  $\text{O}_{2,\text{g}}$  had no effect on nucleation and growth in Ag(100) homoepitaxy.<sup>21</sup> Those experiments were done under somewhat different conditions, i.e., *simultaneous*  $\text{O}_{2,\text{g}}$  exposure and Ag deposition, and the impact on nucleation was measured with HRLEED. This was done using the same HRLEED (lower-step-density) crystal mentioned in Sec. III A. Presumably, a negligible amount of  $\text{O}_{\text{ad}}$  had accumulated at early times, when island nucleation was occurring.

### E. Comparison with other systems

Let us compare the effect that  $\text{O}_{\text{ad}}$  exerts on nucleation in this system, to the effect exerted by other surfactants in other simple, homoepitaxial systems. [Elsewhere, we present evidence that  $\text{O}_{\text{ad}}$  is a good surfactant on Ag(100), and so this is a relevant context.] One observation is clear: Other surfactants affect the value of  $N_{\text{av}}$  strongly but differently. Thus,  $\text{Sb}_{\text{ad}}$  on Ag(111) and Ag(100),<sup>4,10</sup> and  $\text{O}_{\text{ad}}$  on Pt(111),<sup>11</sup> all cause  $N_{\text{av}}$  to *increase*, while  $\text{O}_{\text{ad}}$  on Ag(100) causes  $N_{\text{av}}$  to *decrease*. The two metal (111) systems have been studied in most detail. There, the interpretation is that the surfactant exerts two effects simultaneously: it impedes diffusion of metal atoms across the terraces (i.e., it raises the terrace diffusion barrier), *and* it lowers the step-edge barrier.<sup>4,10</sup> The first half of this explanation cannot apply in our system, because quantitative evaluation of  $N_{\text{av}}$  vs  $F$  [Fig. 3 and Eq. (2)] and  $N_{\text{av}}$  vs  $T$  (Fig. 4) reveals that the activation barrier to diffusion of the diffusing species *must* be *lower* in the presence of  $\text{O}_{\text{ad}}$  than in its absence. The second part is only tangentially relevant, since we do not believe that the step-edge barrier for  $\text{Ag}_{\text{ad}}$  is important, but rather the step-edge barrier for a different species.

In short, the model for our system differs fundamentally from those proposed in other systems because in our model, *the surfactant changes the nature of the diffusing and nucleating species*, rather than simply modifying energetic barriers within a preexisting mechanism of metal–adatom nucleation. This is consistent with the fact that the fundamental effect of the surfactant in our system is also different; it causes  $N_{\text{av}}$  to decrease, relative to the clean surface, whereas in the other three systems cited above it causes  $N_{\text{av}}$  to increase.

## V. CONCLUSIONS

Island nucleation on Ag(100) at 250 K is impeded by preexposure to  $\text{O}_{2,\text{g}}$ . In order for this to occur, the  $\text{O}_{2,\text{g}}$  must adsorb and dissociate.  $\text{O}_{2,\text{ad}}$  dissociates at kink sites at steps. Hence, step density is important in determining the extent of the effect of  $\text{O}_{2,\text{g}}$  preexposure.

The effect of oxygen is to decrease the average island density. Analysis of average island density as a function of Ag flux reveals a threefold increase in the flux exponent ( $\chi$ )

from  $O_{2,g}$  preexposure. The temperature dependence of island density, with preexposure to  $O_{2,g}$ , gives an apparent energy ( $E$ ) of 0.10 eV in the range 300–220 K.

We hypothesize that  $Ag_mO_{ad}$  is the nucleating species, and its nucleation is highly reversible (critical size  $i \gg 1$ ). Small aggregates of this species may also be mobile. Its activation energy for terrace diffusion ( $E_d$ ) is  $\leq 0.11$  eV, much lower than the value of 0.45 eV for  $Ag_{ad}$  on clean  $Ag(100)$ . Two-step deposition experiments indicate that the oxygen-containing species that is generated at step edges, as well as the  $Ag_mO_{ad}$  species that mediates nucleation, diffuse freely across terrace steps, as well as across terraces.

## ACKNOWLEDGMENTS

The authors thank Kyle Caspersen for useful discussions, and for performing the simulations cited in Ref. 45. We thank Cynthia Jenks for assistance with analysis of island size distributions. This work was supported by NSF Grant CHE-0078596, and performed at Ames Laboratory, which is operated for the USDOE by Iowa State University under Contract No. W-7405-Eng-82.

- <sup>1</sup>H. A. van der Vegt, H. M. van Pinxteren, M. Lohmeier, E. Vlieg, and J. M. C. Thornton, *Phys. Rev. Lett.* **68**, 3335 (1992).
- <sup>2</sup>K. Fukutani, *Surf. Sci.* **281**, 285 (1993).
- <sup>3</sup>H. Wolter, M. Schmidt, and K. Wandelt, *Surf. Sci.* **298**, 173 (1993).
- <sup>4</sup>J. Vrijmoeth, H. A. van der Vegt, J. A. Meyer, E. Vlieg, and R. J. Behm, *Phys. Rev. Lett.* **72**, 3843 (1994).
- <sup>5</sup>H. A. van der Vegt, J. Alvares, X. Torrelles, S. Ferrer, and E. Vlieg, *Phys. Rev. B* **52**, 17443 (1995).
- <sup>6</sup>V. Fiorentini, S. Oppo, and M. Scheffler, *Appl. Phys. A: Mater. Sci. Process.* **60**, 399 (1995).
- <sup>7</sup>H. A. van der Vegt, W. J. Huisman, P. B. Howes, T. S. Turner, and E. Vlieg, *Surf. Sci.* **365**, 205 (1996).
- <sup>8</sup>M. Yata, H. Rouch, and K. Nakamura, *Phys. Rev. B* **56**, 10579 (1997).
- <sup>9</sup>W. F. Egelhoff, Jr., *Surf. Sci.* **402–404**, 32 (1998).
- <sup>10</sup>H. A. van der Vegt, J. Vrijmoeth, R. J. Behm, and E. Vlieg, *Phys. Rev. B* **57**, 4127 (1998).
- <sup>11</sup>S. Esch, M. Hohage, T. Michely, and G. Comsa, *Phys. Rev. Lett.* **72**, 518 (1994).
- <sup>12</sup>H. A. van der Vegt, W. J. Huisman, P. B. Howes, and E. Vlieg, *Surf. Sci.* **330**, 101 (1995).
- <sup>13</sup>P. A. Thiel and J. W. Evans, *J. Phys. Chem.* **104**, 1663 (2000).
- <sup>14</sup>M. Kalff, G. Comsa, and T. Michely, *Phys. Rev. Lett.* **81**, 1255 (1998).
- <sup>15</sup>E. Kopatzki, S. Guenther, W. Nichtl-Pecher, and R. J. Behm, *Surf. Sci.* **284**, 154 (1992).
- <sup>16</sup>F. Buatier de Mongeot, A. Cupolillo, M. Rocca, and U. Valbusa, *Chem. Phys. Lett.* **302**, 302 (1999).
- <sup>17</sup>F. Buatier de Mongeot, A. Cupolillo, U. Valbusa, and M. Rocca, *Chem. Phys. Lett.* **270**, 345 (1997).
- <sup>18</sup>F. Buatier de Mongeot, M. Rocca, A. Cupolillo, U. Valbusa, H. J. Kreutzer, and S. H. Payne, *J. Chem. Phys.* **106**, 711 (1997).
- <sup>19</sup>G. Costantini, F. Buatier de Mongeot, S. Rusponi, C. Boragno, U. Valbusa, L. Vattuone, U. Burghaus, L. Savio, and M. Rocca, *J. Chem. Phys.* **112**, 6840 (2000).
- <sup>20</sup>L. Savio, L. Vattuone, and M. Rocca, *Phys. Rev. Lett.* **87**, 276101 (2001).
- <sup>21</sup>A. R. Layson and P. A. Thiel, *Surf. Sci.* **472**, L151 (2001).
- <sup>22</sup>A. R. Layson, J. W. Evans, and P. A. Thiel, *Phys. Rev. B* **65**, 193409 (2002).
- <sup>23</sup>Specifically, suppose  $O_{ad}$  attached permanently to step edges, but inhibited attachment of  $Ag_{ad}$ . This would increase the density of Ag islands in the depletion zones of step edges, and not affect the density elsewhere, in contrast to our observations.
- <sup>24</sup>M. Rocca, L. Savio, L. Vattuone *et al.*, *Phys. Rev. B* **61**, 213 (2000).
- <sup>25</sup>J. A. Venables, *Philos. Mag.* **27**, 697 (1973), and references therein.
- <sup>26</sup>S. Stoyanov and D. Kashchiev, in *Current Topics in Materials Science*, edited by E. Kaldis (North-Holland, Amsterdam, 1981), Vol. 7, p. 71, and references therein.
- <sup>27</sup>M. Bartelt and J. W. Evans, *Phys. Rev. B* **46**, 12 675 (1992).
- <sup>28</sup>M. C. Bartelt and J. W. Evans, *Surf. Sci.* **298**, 421 (1993).
- <sup>29</sup>C.-M. Zhang, M. C. Bartelt, J.-M. Wen, C. J. Jenks, J. W. Evans, and P. A. Thiel, *Surf. Sci.* **406**, 178 (1998).
- <sup>30</sup>The adatom density satisfies  $dN_1/dt \approx F - s_{av}DN_{av}N_1 \approx 0$  in the steady-state approximation, where  $D$  is the terrace diffusion rate. Thus, one has  $N_{av} \sim (F/D)(N_1)^{-1} \sim F/D$  for highly reversible island formation, where  $N_1$  depends very weakly on  $F$ .
- <sup>31</sup>S. Frank, H. Wedler, R. J. Behm, J. Rottler, P. Maass, K. J. Caspersen, C. R. Stoldt, P. A. Thiel, and J. W. Evans, *Phys. Rev. B* **66**, 155435 (2002).
- <sup>32</sup>L. Bardotti, C. R. Stoldt, C. J. Jenks, M. C. Bartelt, J. W. Evans, and P. A. Thiel, *Phys. Rev. B* **57**, 12544 (1998).
- <sup>33</sup>C. R. Stoldt, C. J. Jenks, P. A. Thiel, A. M. Cadilhe, and J. W. Evans, *J. Chem. Phys.* **111**, 5157 (1999).
- <sup>34</sup>M. H. Langelaar, M. Breeman, and D. O. Boerma, *Surf. Sci.* **352/354**, 597 (1996).
- <sup>35</sup>B. D. Yu and M. Scheffler, *Phys. Rev. B* **55**, 13916 (1997).
- <sup>36</sup>J. Villain, A. Pimpineli, L. Tang, and D. E. Wolf, *J. Phys. I* **2**, 2107 (1992).
- <sup>37</sup>D. E. Wolf, in *Scale Invariance, Interfaces, and Non-Equilibrium Dynamics*, edited by M. Droz, A. J. McKane, J. Vannimenus, and D. E. Wolf (NATO ASI Series (Plenum, New York, 1994).
- <sup>38</sup>M. C. Bartelt, S. Gunther, E. Kopatzki, R. J. Behm, and J. W. Evans, *Phys. Rev. B* **53**, 4099 (1996).
- <sup>39</sup>I. Furman and O. Biham, *Phys. Rev. B* **55**, 7917 (1997).
- <sup>40</sup>S. Liu, L. Bonig, and H. Metiu, *Phys. Rev. B* **52**, 2907 (1995).
- <sup>41</sup>K. Pohl, J. de la Figuera, M. C. Bartelt, N. C. Bartelt, P. J. Feibelman, R. Q. Hwang, *Bull. Am. Phys. Soc.* **44**, 1716 (1999).
- <sup>42</sup>P. Feibelman, *Phys. Rev. Lett.* **85**, 606 (2000).
- <sup>43</sup>K. J. Caspersen, C. R. Stoldt, A. R. Layson, M. C. Bartelt, P. A. Thiel, and J. W. Evans, *Phys. Rev. B* **63**, 085401 (2001).
- <sup>44</sup>K. J. Caspersen, A. R. Layson, C. R. Stoldt, V. Fournée, P. A. Thiel, and J. W. Evans, *Phys. Rev. B* **65**, 193407 (2002).
- <sup>45</sup>K. J. Caspersen (unpublished).